



# Prognostic Model for Corrosion-Inhibition of Mild Steel in Hydrochloric Acid by Crushed Leaves of Voacanga Africana

Charles Nwachukwu Anyakwo<sup>1</sup>, Agha Inya Ndukwe<sup>2</sup>

<sup>1</sup>Department of Materials and Metallurgical Engineering, Federal University of Technology, Owerri, Nigeria

<sup>2</sup>Department of Metallurgical Engineering Technology, Akanu Ibiam Federal Polytechnic Unwana, Afikpo, Nigeria

## Email address:

ndukweaghainya@yahoo.com (A. I. Ndukwe)

## To cite this article:

Charles Nwachukwu Anyakwo, Agha Inya Ndukwe. Prognostic Model for Corrosion-Inhibition of Mild Steel in Hydrochloric Acid by Crushed Leaves of Voacanga Africana. *International Journal of Computational and Theoretical Chemistry*. Vol. 5, No. 3, 2017, pp. 30-41. doi: 10.11648/j.ijctc.20170503.12

**Received:** June 2, 2017; **Accepted:** June 15, 2017; **Published:** July 26, 2017

---

**Abstract:** The weight-loss technique was used to study the inhibition of the corrosion of mild steel in 0.7M, 1.2M and 2.2M HCl by thoroughly crushed fresh-leaves of Voacanga Africana. The corrosion rate was observed to increase with increase in the concentration of acid. The maximum inhibition efficiency of 69.80% was obtained when thoroughly crushed leaves of Voacanga Africana was added at 15g per litre of 0.7M HCl with a corresponding decrease in corrosion rate from 2.6487mg.cm<sup>-2</sup>.h<sup>-1</sup> to 1.3684mg.cm<sup>-2</sup>.h<sup>-1</sup>. The prediction of the corrosion rate by the artificial neural network gave a minimal error and was closer to the experimental corrosion-rate value in comparison with the prediction by multiple regression. Upon the variation of temperature between 298K and 358K, the activation energy obtained for the corrosion of mild steel in the blank solution of 0.7M HCl was 20,908.68J while the addition of Voacanga Africana's crushed leaves at 15g per litre of 0.7M HCl increased the activation energy to 26,710.26J. The corrosion inhibition of mild steel in hydrochloric acid by the addition of the crushed plant-leaves is in agreement with the Langmuir adsorption isotherm with R<sup>2</sup> = 0.992.

**Keywords:** Voacanga Africana, Crushed Plant-Leaves, Hydrochloric Acid, Artificial Neural Network, Multiple Regression, Inhibition Efficiency, Corrosion Rate, Mild Steel

---

## 1. Introduction

Corrosion is the deterioration of a metal owing to its reaction with the environment [1, 2]. This development involves a gradual reversion to the more stable state such as oxide, sulphide or carbonate [3]. Allowing corrosion to unabatedly occur may lead to catastrophic consequences. However, corrosion can be prevented through cathodic protection, anodic protection, addition of inhibitors, coating and proper selection of materials. The method of corrosion prevention by the addition of inhibitors is pertinent to this study.

An inhibitor should be able to reduce the degradation of a metal when added in small amount to the corrosive environment. Benzimidazole and triazole derivatives are well known corrosion inhibitors that showed more than 97% of inhibition against acid corrosion of mild steel [4], but they

are also known for their toxicity [5, 6, 7]. Notably, the toxic nature of the known effective inhibitors of arsenate- and chromate-based has necessitated the search for an alternative inhibitor that would not only be efficacious but environmentally friendly. Previous research has revealed the effectiveness of some plant-extracts in inhibiting the corrosion of metals and alloys. This present work aims at investigating the effectiveness of thoroughly crushed leaves of Voacanga Africana in reducing the hydrochloric acid-induced corrosion of mild steel.

The various species of the Voacanga genus are evergreen trees. They grow to a height of 6m with a spread of 2m, but are usually kept smaller in cultivation. The stem is erect; the leaves are broadly oval and up to 30cm long. The berries contain several brown seeds which are irregularly shaped, and grow in a cluster that sometimes can resemble a brain. The various species of the genus are very similar to one

another, featuring yellow or white flowers with five united petals [8, 9]. A native of the West African rainforests, *Voacanga Africana* prefers rich soils in protected sunny to shady areas, and is tender to drought and frost. Propagation is from fresh seed or cuttings. Fresh seeds germinate much more quickly than older seeds [10].

The corrosion inhibition data are better understood by developing a mathematical model. Predictive models are produced using multiple regression and artificial neural network (ANN). In multiple regression, the relationship between the dependent variable (which is the corrosion rate in this study) and three independent variables (conc. of acid, quantity of crushed leaves and time of exposure) is evaluated. On the other hand, the working principle of the artificial neural network is similar to that of human nervous system [11].

## 2. Methodology

### 2.1. Preparation of Crushed Leaves

Fresh leaves of *Voacanga Africana* were obtained within the surrounding of the Federal University of Technology Owerri. The leaves were thoroughly crushed with a manual blender before being added to different concentrations of acid at 15g per litre, 30g per litre and 45g per litre of 0.7M, 1.2M and 2.2M HCl.

### 2.2. Fabrication of Mild Steel Coupons

The Mild steel ((wt %) C=0.20%, Zn=0.75%, Ti=0.28, Mn=0.23%, S=0.04%, P=0.035% and Fe balance) coupons of 4cm by 4cm by 0.15cm dimensions were press cut from a sheet metal using a foot shear cutting machine. The mild steel coupons were ground down with coarse and fine emery papers and later cleaned with acetone before their initial weights were determined by the Ohaus electronic weighing balance.

### 2.3. Weight-Loss Technique

The weighed coupons were immersed in various

$$R_{\text{corr}} = k_0 + f_1(\text{time of exposure}) + f_2(\text{conc. of acid}) + f_3(\text{quantity of crushed leaves}) \quad (3)$$

Where,

$k_0$  = Intercept on  $R_{\text{corr}}$  axis.

$f_1$  = Change in  $R_{\text{corr}}$  for each 1 increment change in time of exposure.

$f_2$  = Change in  $R_{\text{corr}}$  for each 1 increment change in conc. of acid.

$f_3$  = Change in  $R_{\text{corr}}$  for each 1 increment change in quantity of crushed leaves.

### 2.4.2. Artificial Neural Network (ANN)

Artificial neural network imitates the human brain in data analysis. It consists of a number of very simple and highly interconnected processors, also called neurons, which are similar to the biological neurons in the brain [13]. Figure 1

concentrations of hydrochloric acid to which different quantities of crushed leaves of *Voacanga Africana* had been added at 15g per litre, 30g per litre and 45g per litre of 0.7M, 1.2M and 2.2M HCl. Another experimental set-up which did not contain any inhibitor was prepared for the purpose of comparison. In every hour, a coupon was withdrawn from the study environment, thoroughly cleaned with acetone and re-weighed to figure out the final weight. The experimentation lasted for eight hours. The above experimental procedure was repeated by varying the temperature between 298K and 358K.

The rate at which the mild steel corroded was computed using the formula [9, 12]:

$$\text{Corrosion rate, } R_{\text{corr}} = w/(A.t) \quad (1)$$

Where,

$w$  = Weight-loss.

$A$  = Exposed area.

$t$  = Time of exposure.

The inhibition efficiency occasioned by the addition of thoroughly crushed leaves of *Voacanga Africana* to the corrodent was obtained by the relationship:

$$\text{Inhibition efficiency, I.E (\%)} = (R_{\text{corr1}} - R_{\text{corr2}}/R_{\text{corr1}}) * 100 \quad (2)$$

Where,

$R_{\text{corr1}}$  = Corrosion rate of the uninhibited environment.

$R_{\text{corr2}}$  = Corrosion rate of the inhibited environment.

### 2.4. Development of Predictive Model

#### 2.4.1. Multiple Regression (MR)

Multiple regression is a statistical tool that generates a mathematical model by evaluating the relationship between the dependent variable and two or more independent variables. In this study, the dependent variable is the corrosion rate ( $\text{mg.cm}^{-2}.\text{h}^{-1}$ ) whilst the three independent variables are conc. of acid (M), quantity of crushed leaves (g) and time of exposure (h). Using the principle of multiple regression, the model can be obtained by employing the formula:

illustrates the artificial neural network for the prediction of corrosion inhibition of mild steel in hydrochloric acid by thoroughly crushed leaves of *Voacanga Africana*.

The artificial network neurons are joined by weighted links which pass signals from one neuron to another as displayed in Figure 2. Each neuron obtains several signals from its input links, computes a new activation level and transmits it as an output signal. The neuron calculates the weighted sum of the input signals and compares the result with a threshold value. The other input to the neuron,  $d_j$  is referred to as the bias, which is an arbitrary selected value that oversees the input of the network as depicted in equation (4) [14].

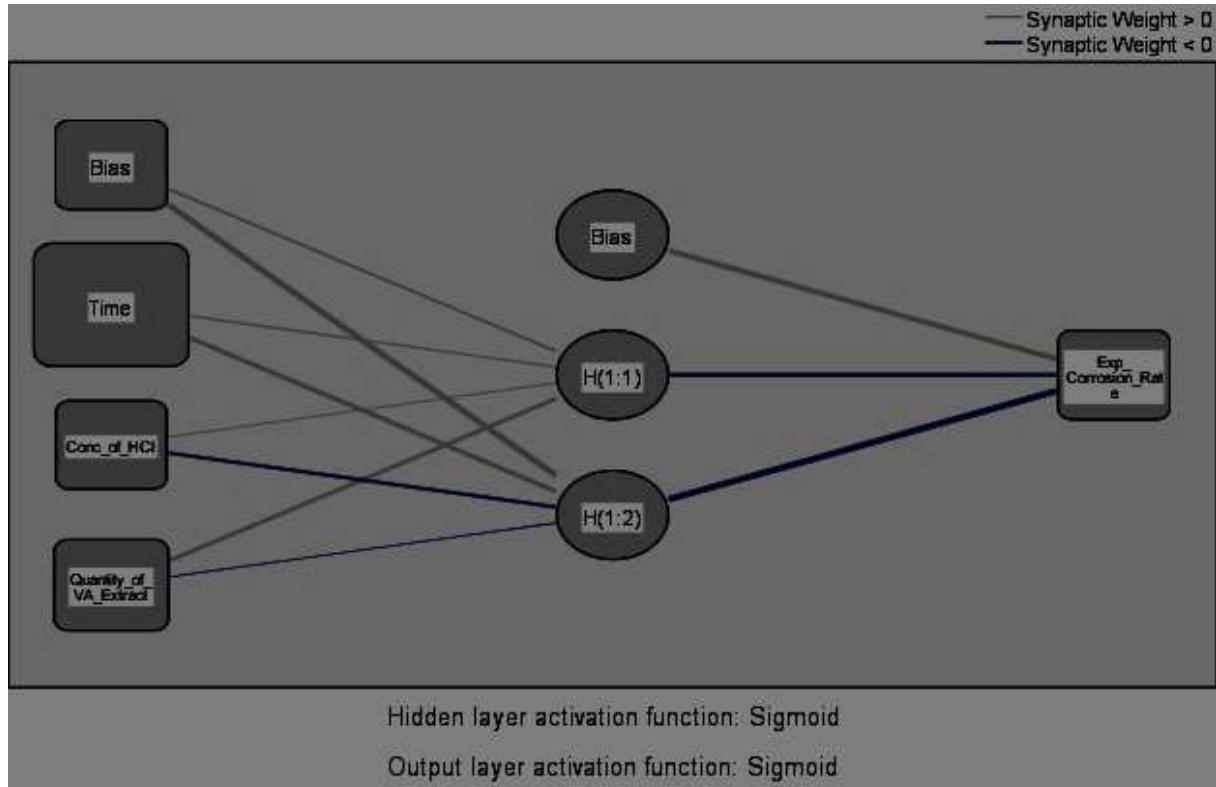


Figure 1. Artificial neural network for the prediction of corrosion inhibition of mild steel in hydrochloric acid by thoroughly crushed leaves of Voacanga Africana.

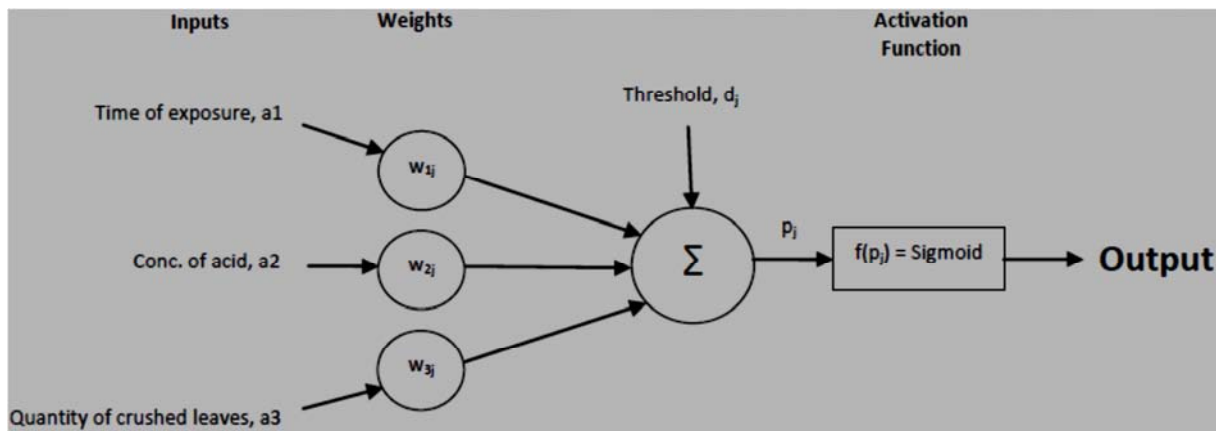


Figure 2. Schematic representation of the neuron.

According to [13], the neuron output is -1 if the net input is less than the threshold. But if the net input is greater than or equal to the threshold, the neuron becomes activated and its output attains a value +1. The net input of the network is computed by using the equation below:

$$p_j = \sum(a_i \cdot w_{ij}) + d_j \tag{4}$$

- Where,
- $p_j$  = Net input.
- $a_i$  = Input of unit.
- $w_{ij}$  = Weight.
- $d_j$  = Bias of the unit.

The sigmoid function,  $f(p_j)$  transforms the input, which can have any value between plus and minus infinity, into a

reasonable value in the range between 0 and 1 as given in equation (5) [14]. Neurons with this function are used in the back-propagation networks [13].

$$f(p_j) = 1/(1+e^{-p_j}) \tag{5}$$

Where,  
 $p_j$  = Net input.

### 2.4.3. Analysis of Error in Prediction

The importance of error analysis in prediction is to investigate how close the predicted value is to the actual or experimental value. The error in prediction can be obtained by using the mean standard error (MSE) and the mean absolute error (MAE) whose formulae are stated below:

$$\text{MSE} = 1/N \sum (C_i - D_i)^2 \quad (6) \quad C_i = \text{Predicted value.}$$

$$\text{MAE} = 1/N \sum (C_i - D_i) \quad (7) \quad D_i = \text{True value.}$$


Where,

$N$  = Number of samples.


### 3. Results

**Table 1.** Effect of addition of thoroughly crushed leaves of *Voacanga Africana* on the corrosion of mild steel immersed in different concentrations of hydrochloric acid.


Exposure Time (Hours)	0.7M HCl		1.2M HCl		2.2M HCl	
	CR (mg.cm <sup>-2</sup> .h <sup>-1</sup> )	I.E (%)	CR (mg.cm <sup>-2</sup> .h <sup>-1</sup> )	I.E (%)	CR (mg.cm <sup>-2</sup> .h <sup>-1</sup> )	I.E (%)
Addition of thoroughly crushed leaves of <i>Voacanga Africana</i> at 15g per litre of HCl						
1	2.6487	55.42	1.6351	28.46	4.5307	24.01
2	1.8646	69.16	1.0078	35.74	2.2131	38.05
3	1.3989	66.50	0.7900	28.89	1.4986	38.50
4	1.4137	66.20	0.7493	36.25	1.1668	38.76
5	1.4214	71.80	0.6936	41.41	1.0647	32.11
6	1.3684	75.70	0.6661	36.38	0.8853	34.24
7	1.3924	74.85	0.5838	44.12	0.7667	36.19
8	1.3934	78.74	0.5820	37.26	0.7497	34.92
Average	0.5115	69.80	0.8385	36.06	1.6095	34.60
Addition of thoroughly crushed leaves of <i>Voacanga Africana</i> at 30g per litre of HCl						
1	1.0688	59.65	1.8007	21.22	3.8686	35.12
2	0.6651	64.33	0.7900	49.63	2.1492	39.84
3	0.5547	60.35	0.6215	44.05	1.6167	33.65
4	0.5322	62.35	0.7166	39.03	0.8394	55.94
5	0.4560	67.92	0.6302	46.76	0.6366	59.41
6	0.5450	60.17	0.5087	51.41	0.6399	52.47
7	0.4373	68.59	0.3004	71.24	0.6659	44.58
8	0.4358	68.72	0.3264	64.81	0.5525	52.04
Average	0.5869	64.01	0.7118	48.52	0.5525	46.63
Addition of thoroughly crushed leaves of <i>Voacanga Africana</i> at 45g per litre of HCl						
1	0.8974	66.12	0.6354	72.20	3.7930	36.39
2	0.6520	65.03	0.5896	62.41	1.6743	53.13
3	0.5207	62.78	0.2962	73.34	1.2072	50.46
4	0.3340	76.37	0.2127	81.90	0.9817	48.46
5	0.4711	66.86	0.4932	58.34	1.0363	33.92
6	0.4778	65.08	0.4410	57.88	0.8853	34.24
7	0.3925	71.81	0.2996	71.32	0.7277	39.44
8	0.3688	73.53	0.2062	77.77	0.6546	43.17
Average	0.5145	68.45	0.3967	68.65	1.3700	42.40

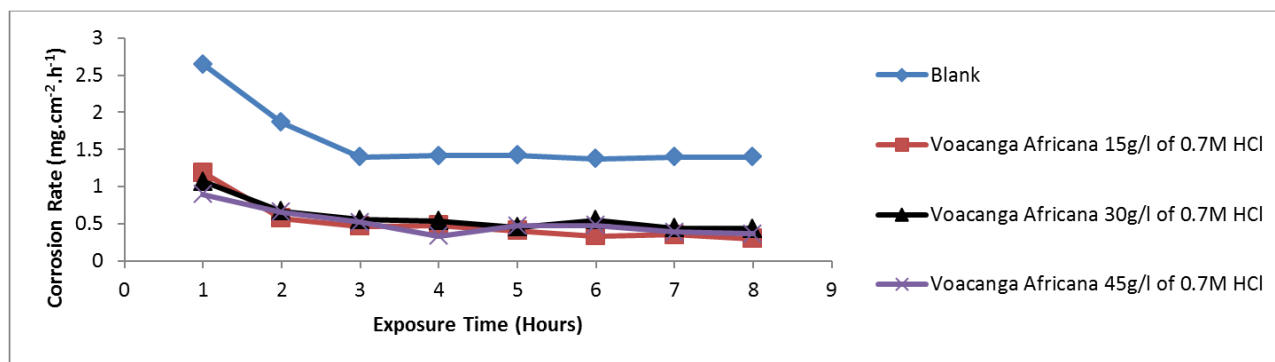

(a)

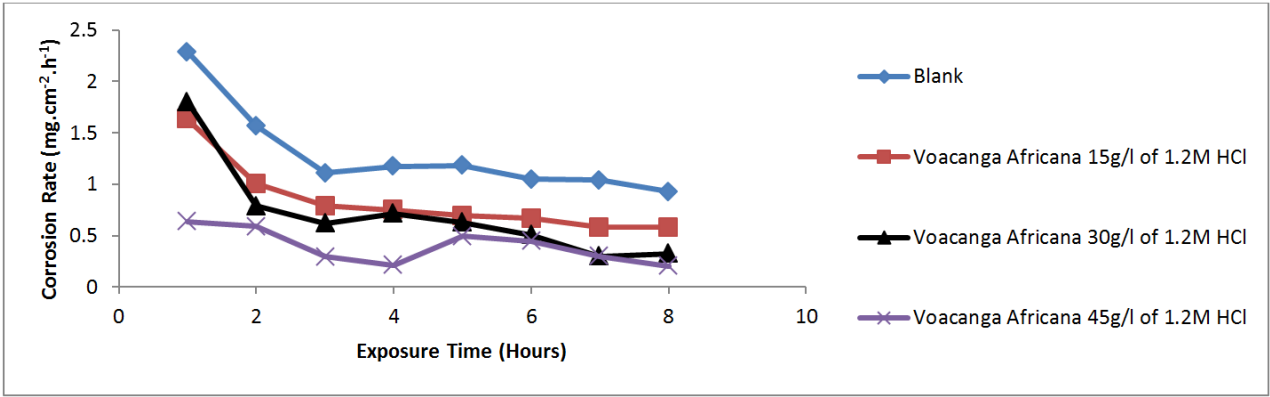


(b)

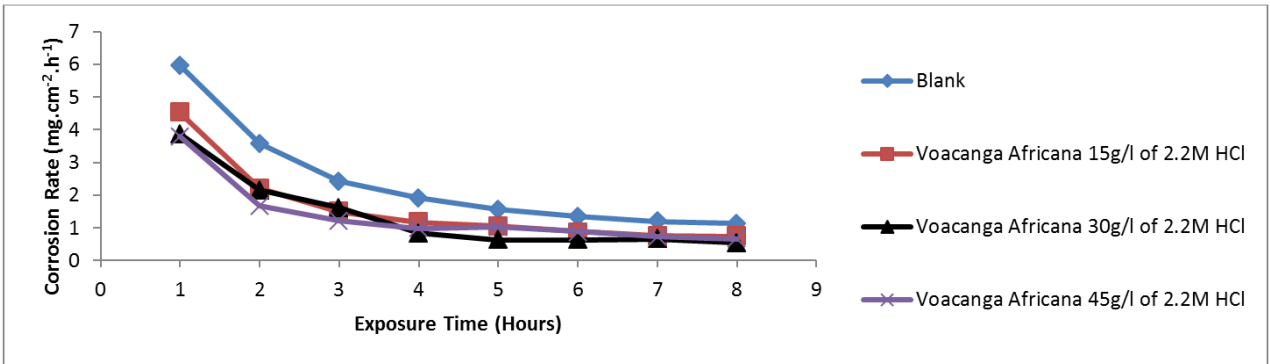


(c)


Figure 3. Effect of addition of thoroughly crushed leaves of Voacanga Africana on corrosion of mild steel coupons immersed at: (a) 15g/l, 30g/l and 45g/l of 0.7M HCl, (b) 15g/l, 30g/l and 45g/l of 1.2M HCl, (c) 15g/l, 30g/l and 45g/l of 2.2M HCl.

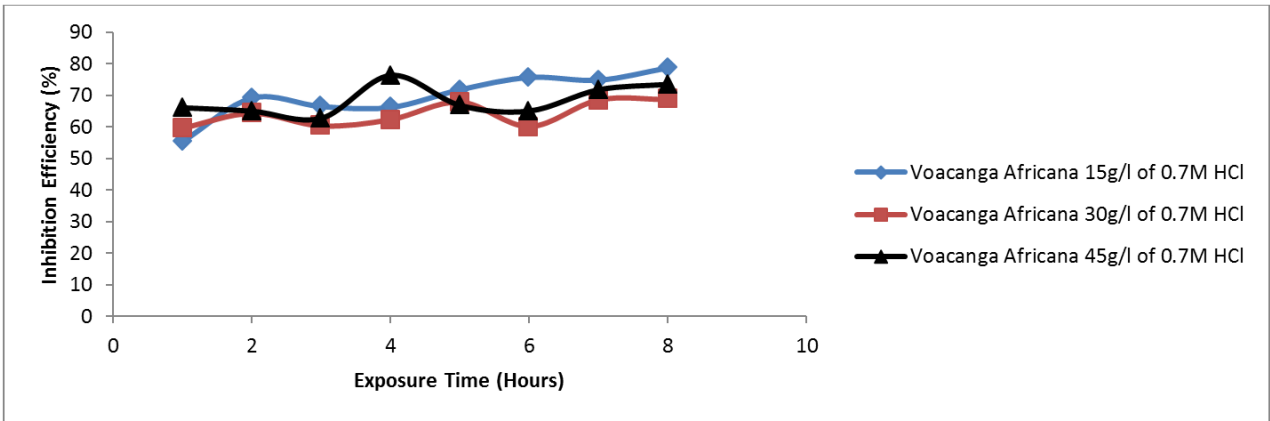

(a)

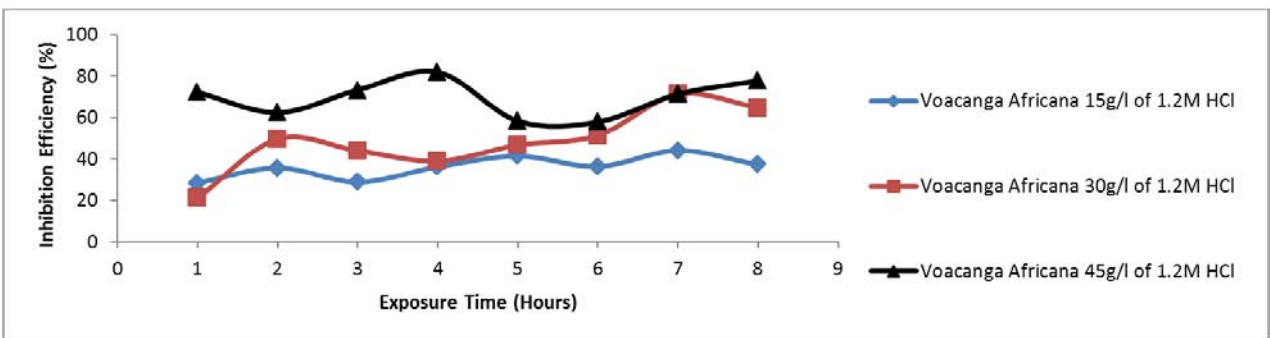

(b)

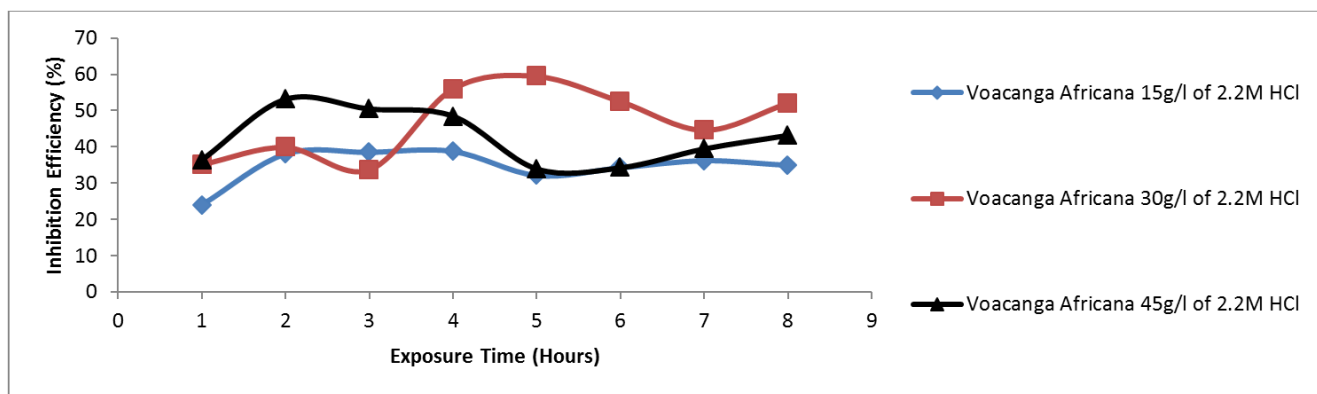

(c)

Figure 4. Voacanga Africana's corrosion inhibition efficiency for mild steel coupons immersed at: (a) 15g/l, 30g/l and 45g/l of 0.7MHCl, (b) 15g/l, 30g/l and 45g/l of 1.2MHCl, (c) 15g/l, 30g/l and 45g/l of 2.2MHCl.

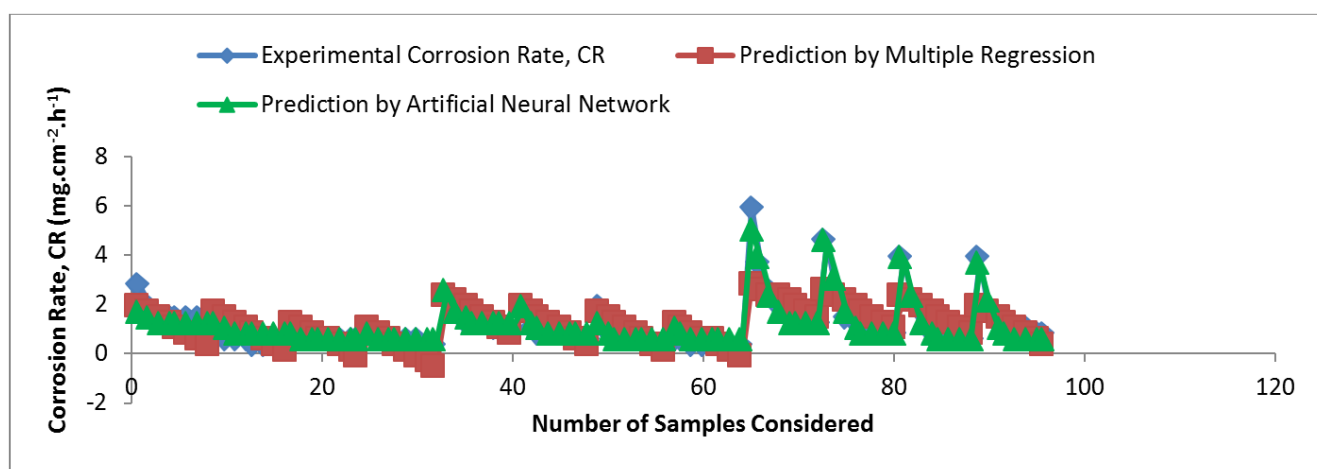


Figure 5. Comparison of error for the prediction of corrosion inhibition of mild steel in hydrochloric acid by thoroughly crushed leaves of Voacanga Africana using multiple regression, MR and artificial neural network, ANN.

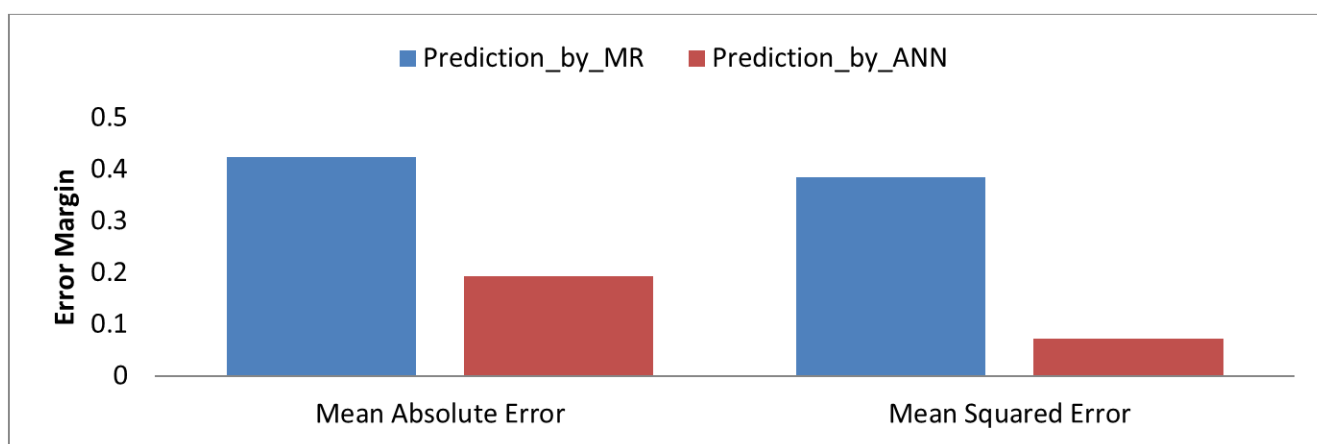


Figure 6. Error graph for the prediction of corrosion inhibition of mild steel in hydrochloric acid by thoroughly crushed leaves of Voacanga Africana using multiple regression, MR and artificial neural network, ANN.

Table 2. Analysis for prediction of corrosion inhibition of mild steel in hydrochloric acid by thoroughly crushed leaves of Voacanga Africana using multiple regression (MR).

	Model Coefficients			
	Constant	Time (h)	Conc. of Acid (M)	Quantity of Crushed Leaves (g)
HCl	1.670	-0.213	0.628	-0.021

**Table 3.** Analysis for the prediction of corrosion inhibition of mild steel in hydrochloric acid by thoroughly crushed leaves of Voacanga Africana using artificial neural network (ANN).

Independent variable importance for the addition of thoroughly crushed leaves of Voacanga Africana in hydrochloric acid		
	Importance	Normalized Importance
Time	0.496	100.0%
Conc_of_HCl	0.242	48.8%
Quantity of VA Extract	0.262	52.8%

*Table 3. Continue.*

Parameter Estimates for the addition of thoroughly crushed leaves of Voacanga Africana in hydrochloric acid			
Predictor		Predicted	
		Hidden Layer 1	Output Layer
		H(1:1)	H(1:2)
Input Layer	(Bias)	1.019	4.542
	Time	0.174	2.282
	Conc_of_HCl	0.056	-1.268
	Quantity_of_VA_Extract	1.949	-0.021
Hidden Layer 1	(Bias)		3.235
	H (1:1)		-1.638
	H (1:2)		-4.541

**Table 4.** Error analysis for the prediction of corrosion inhibition of mild steel in hydrochloric acid by thoroughly crushed leaves of Voacanga Africana using multiple regression, MR and artificial neural network, ANN.


Error	Prediction of CR by Multiple Regression, MR	Prediction of CR by Artificial Neural Network, ANN
Mean Absolute Error	0.423305417	0.193705208
Mean Squared Error	0.384576304	0.071829608

**Table 5.** Effect of variation in temperature on the corrosion of mild steel coupons immersed at 15g of Voacanga Africana's crushed fresh leaves per litre of 0.7M HCl.

Temperature (K)	CR <sub>VA addition</sub> (mg.cm <sup>-2</sup> .h <sup>-1</sup> )	CR <sub>Blank</sub> (mg.cm <sup>-2</sup> .h <sup>-1</sup> )	Log CR <sub>VA addition</sub>	Log CR <sub>Blank</sub>	1/T (K <sup>-1</sup> )
298	0.5115	1.6127	-0.2912	0.2076	0.003356
318	1.7779	5.4985	0.2499	0.7402	0.003145
338	2.6064	6.4186	0.4160	0.8074	0.002959
358	3.3283	7.0779	0.5222	0.8499	0.002793

Slope<sub>Blank</sub> = -1092K<sup>-1</sup>, Slope<sub>VA addition</sub> = -1395K<sup>-1</sup>


Activation Energy, Q<sub>Blank</sub> = 20,908.68J, Activation Energy, Q<sub>VA addition</sub> = 26,710.26J

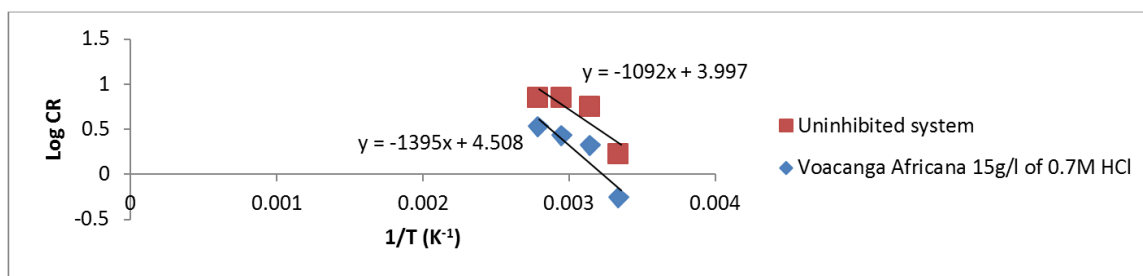


**Figure 7.** Arrhenius plot for the effect of addition of thoroughly crushed leaves of Voacanga Africana on corrosion of mild steel coupons immersed at 15g/l of 0.7M HCl.

**Table 6.** Calculated parameters of four adsorption isotherm models for adsorption of thoroughly crushed fresh leaves of Voacanga Africana onto the surface of mild steel coupons in hydrochloric acid medium.


Adsorption Isotherm							
Langmuir		Freundlich		Temkin		El-Awady	
Slope	R <sup>2</sup>	Slope	R <sup>2</sup>	Slope	R <sup>2</sup>	Slope	R <sup>2</sup>
1.475	0.992	-0.029	0.128	-0.02	0.134	-0.091	0.139
Parameters							
C (g)	Log C	In C	Θ	C/Θ	Log Θ	1-Θ	Log (Θ/1-Θ)
15	1.1761	2.7081	0.6980	21.4900	-0.1561	0.3020	0.3638
30	1.4771	3.4012	0.6401	46.8677	-0.1938	0.3599	0.2501
45	1.6532	3.8067	0.6845	65.7414	-0.1646	0.3155	0.3364

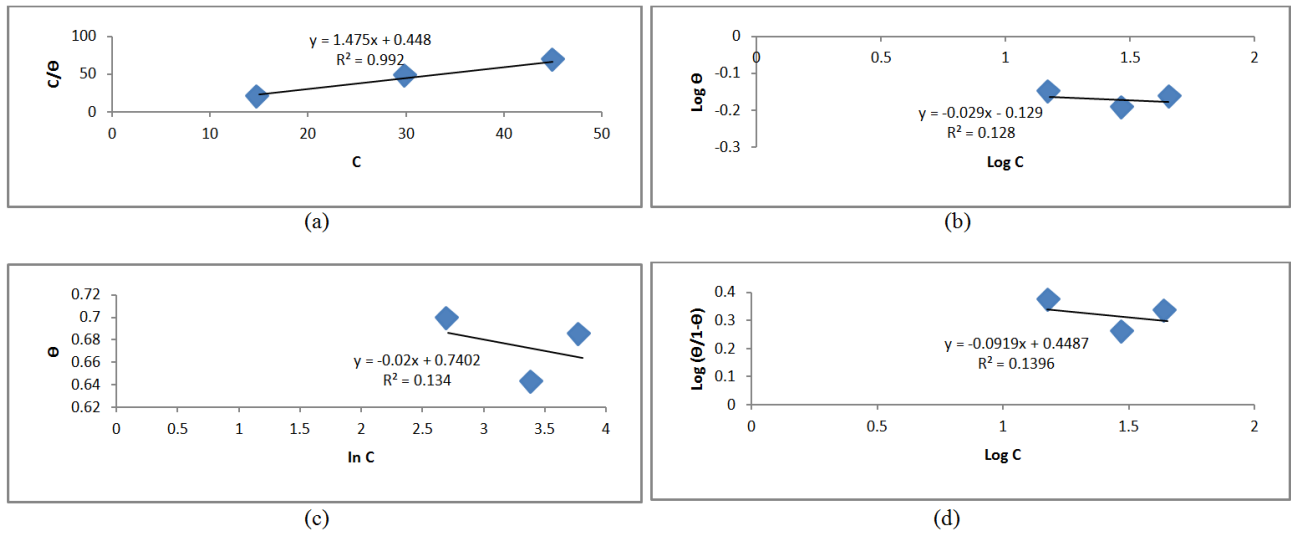

**Figure 8.** Adsorption Isotherm models for adsorption of the crushed leaves of *Voacanga Africana* on the mild steel surface in hydrochloric acid medium: (a) Langmuir adsorption isotherm (b) Freundlich adsorption isotherm (c) Temkin adsorption isotherm (d) El-Awady adsorption isotherm.

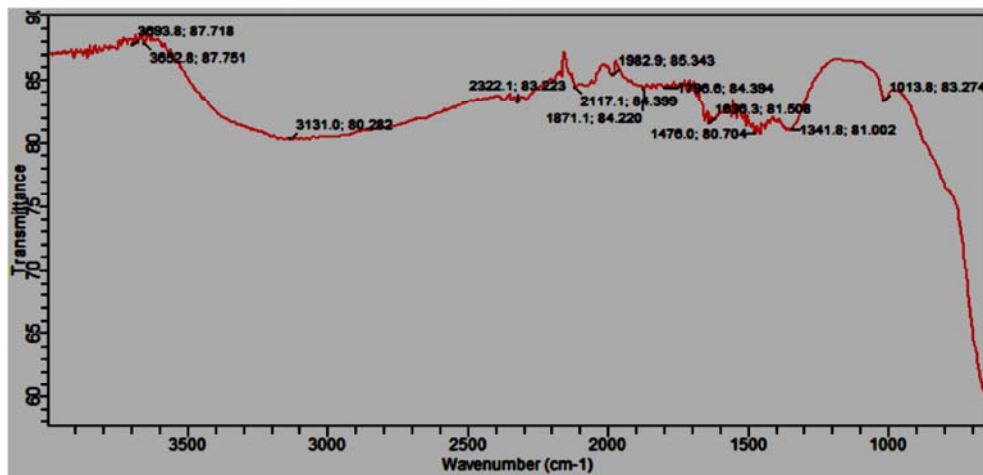

**Figure 9.** FTIR spectrum of film on mild steel surface after immersion in a medium containing thoroughly crushed leaves of *Voacanga Africana* at 30g per litre of 0.7M HCl.

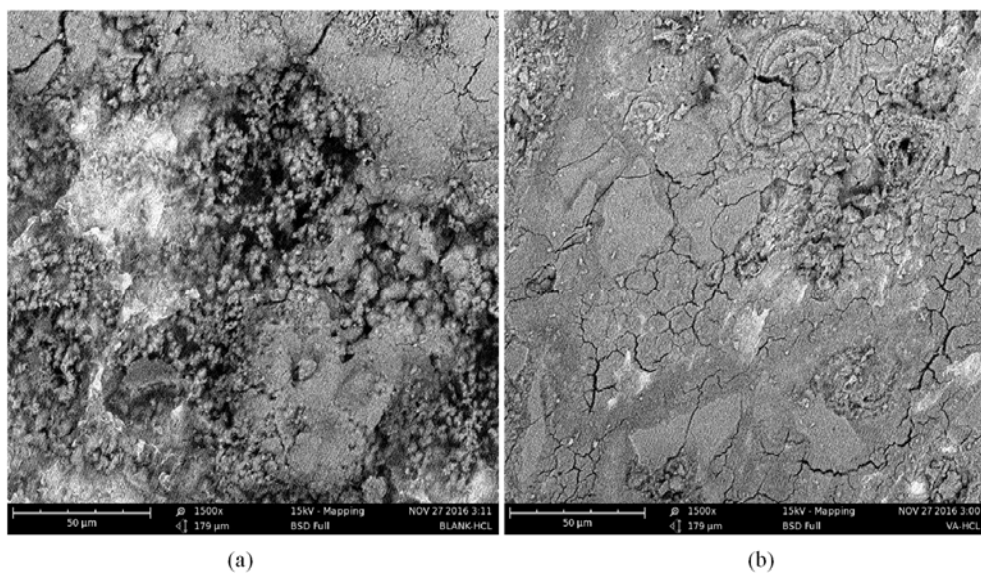

**Figure 10.** SEM features of the corroded mild steel in: (a) the blank solution of 0.7M HCl (b) the presence of thoroughly crushed leaves of *Voacanga Africana* at 30g/l of 0.7M HCl.



## 4. Discussion of Results

### 4.1. Effect of Addition of Thoroughly Crushed Leaves of Voacanga Africana on the Corrosion of Mild Steel Coupons Immersed in Hydrochloric Acid Solution

The average corrosion rate, CR and inhibition efficiency, I.E in the order CR (I.E) as presented in Table 1 for the addition of Voacanga Africana's crushed leaves at 15g per litre of 0.7M, 1.2M and 2.2M HCl gave the following: 0.5115mg.cm<sup>-2</sup>.h<sup>-1</sup> (69.80%) in 0.7M HCl; 0.8385mg.cm<sup>-2</sup>.h<sup>-1</sup> (36.06%) in 1.2M HCl and 1.6095mg.cm<sup>-2</sup>.h<sup>-1</sup> (34.60%) in 2.2M HCl. As the addition of the crushed leaves was increased to 30g per litre of various acid concentrations, the corresponding average corrosion rate and inhibition efficiency were: 0.5869mg.cm<sup>-2</sup>.h<sup>-1</sup> (64.01%) in 0.7M HCl; 0.7118mg.cm<sup>-2</sup>.h<sup>-1</sup> (48.52%) in 1.2M HCl and 0.5525mg.cm<sup>-2</sup>.h<sup>-1</sup> (46.63%) in 2.2M HCl. Further addition of the crushed leaves at 45g per litre of different acid concentrations gave the following average corrosion rate and inhibition efficiency: 0.5145mg.cm<sup>-2</sup>.h<sup>-1</sup> (68.45%) in 0.7M HCl; 0.3967mg.cm<sup>-2</sup>.h<sup>-1</sup> (68.65%) in 1.2M HCl and 1.3700mg.cm<sup>-2</sup>.h<sup>-1</sup> (42.40%) in 2.2M HCl. The addition of thoroughly crushed leaves of Voacanga Africana reduced the corrosion of mild steel coupons in hydrochloric acid medium. The corrosion rate was observed to increase with increase in the concentration of acid whilst the inhibition efficiency improved with time.

$$CR_{VA \text{ in HCl by MR}} = 1.670 - 0.213(\text{time}) + 0.628(\text{conc. of acid}) - 0.021(\text{quantity of crushed leaves}) \quad (8)$$

On the other hand, the prediction of the experimental corrosion rate of mild steel by artificial neural network revealed the importance of the following independent variables: (time of exposure (h), concentration of acid (M) and quantity of crushed leaves (g)) in the prediction of the dependent variable (Corrosion rate, CR (mg.cm<sup>-2</sup>.h<sup>-1</sup>)) as illustrated in Table 3. The time of exposure was found to largely influence the prediction of the corrosion rate by 49.6%, followed by the quantity of crushed leaves, 26.2% and finally the concentration of acid, 24.2%.

The comparison of error results for the prediction of corrosion inhibition of mild steel by Voacanga Africana's crushed leaves in hydrochloric acid using multiple regression and artificial neural network are presented in Table 4 and displayed in Figures 5 and 6. The results show that predictions by the artificial neural network gave a minimal error and were closer to the experimental corrosion rate values in comparison with predictions by multiple regression.

### 4.3. Effect of Variation in Temperature on the Corrosion of Mild Steel Coupons Immersed at 15g of Voacanga Africana's Thoroughly Crushed Leaves Per Litre of 0.7M HCl

The result of the variation in temperature between 298K and 358K on the corrosion of mild steel without and with the addition of thoroughly crushed leaves of Voacanga Africana

The corrosion rate–time curves for the mild steel coupons dipped in 0.7M, 1.2M and 2.2M HCl in the presence and absence of Voacanga Africana's crushed leaves are displayed in Figure 3. The corrosion-rate curves were observed to decrease progressively as the exposure time increased. On the other hand, the inhibition efficiency–time curves for the corrosion inhibition of mild steel coupons occasioned by the addition of Voacanga Africana's crushed leaves at 15g per litre, 30g per litre and 45g per litre of 0.7M, 1.2M and 2.2M HCl are shown in Figure 4. The inhibition efficiency curves increased as the experimentation progressed. The maximum inhibition efficiency of 69.80% was obtained when thoroughly crushed leaves of Voacanga Africana was added at 15g per litre of 0.7M HCl with a corresponding decrease in corrosion rate from 2.6487mg.cm<sup>-2</sup>.h<sup>-1</sup> to 1.3684mg.cm<sup>-2</sup>.h<sup>-1</sup>.

### 4.2. Prediction of Corrosion Inhibition of Mild Steel in Hydrochloric Acid by Thoroughly Crushed Leaves of Voacanga Africana

Multiple regression and artificial neural network were used to predict the corrosion inhibition of mild steel in hydrochloric acid by Voacanga Africana's crushed leaves. The predicted values are illustrated in Appendix 1. Using multiple regression as presented in Table 2, the predictive equation for the corrosion inhibition of mild steel by thoroughly crushed leaves of Voacanga Africana in hydrochloric acid medium is stated below:

at 15g per litre of 0.7M HCl is presented in Table 5 and displayed in Figure 7. The activation energy obtained for the corrosion of mild steel in the blank solution of 0.7M HCl was 20,908.68J while the addition of Voacanga Africana's crushed leaves at 15g per litre of 0.7M HCl increased the activation energy to 26,710.26J. The higher value of activation energy obtained by the introduction of the crushed leaves of Voacanga Africana to the corrodent suggests that more energy needs to be attained before further corrosion can take place.

### 4.4. Adsorption Isotherm for the Corrosion Inhibition of Mild Steel in Hydrochloric Acid by Thoroughly Crushed Leaves of Voacanga Africana

Langmuir, Freundlich, Temkin and El-Awady adsorption isotherm models were tested and presented in Table 6 and Figure 8 for the corrosion inhibition of mild steel in hydrochloric acid by thoroughly crushed leaves of Voacanga Africana. Of all the tested models, only the Langmuir adsorption isotherm ( $R^2 = 0.992$ ) was obeyed. This development reveals that corrosion inhibition was achieved by the adsorption of a monolayer of the inhibitive constituents of Voacanga Africana's crushed leaves on the surface of mild steel. The Langmuir adsorption isotherm model is expressed by the relationship:

$$C_{\text{inhibitor}}/\Theta = C_{\text{inhibitor}} + 1/K \quad (9)$$

Where,

$C_{inhibitor}$  = Concentration of the inhibitor.

$\theta$  = Fraction of surface coverage.

$k$  = Equilibrium constant for the adsorption process.

#### 4.5. FTIR Analysis of the Corrosion Inhibition of Mild Steel in Hydrochloric Acid by Thoroughly Crushed Leaves of Voacanga Africana

The FTIR spectrum of the adhered constituents of Voacanga Africana's crushed leaves on the surface of mild steel coupon immersed at 30g per litre of 0.7M HCl for eight hours is shown in Figure 9. The O–H functional group is spotted around  $3652.8\text{cm}^{-1}$ . The presence of carbon-carbon triple bond of alkynes is indicated at  $2117.8\text{cm}^{-1}$ . The display of a sharp band around the frequency,  $2117.8\text{cm}^{-1}$  reveals a very polar functional group. The amide functional group of C=O bond is found at  $1676\text{cm}^{-1}$  whilst the two spikes around  $1676\text{cm}^{-1}$  depicts the existence of primary amides.

#### 4.6. SEM Micrograph for the Corrosion Inhibition of Mild Steel in Hydrochloric Acid by Thoroughly Crushed Leaves of Voacanga Africana

The SEM image shows that the deterioration of the surface of mild steel in an uninhibited solution of 0.7M HCl is not uniform (Figure 10(a)) but, is somewhat protected by the

addition of thoroughly crushed leaves of Voacanga Africana at 30g per litre of 0.7M HCl as shown in Figure 10(b).

## 5. Conclusion

The maximum inhibition efficiency of 69.80% was obtained when thoroughly crushed leaves of Voacanga Africana was added at 15g per litre of 0.7M HCl with a corresponding decrease in corrosion rate from  $2.6487\text{mg.cm}^{-2}.\text{h}^{-1}$  to  $1.3684\text{mg.cm}^{-2}.\text{h}^{-1}$ . Predictions by the artificial neural network gave a minimal error and were closer to the experimental corrosion-rate values in comparison with predictions by multiple regression. The activation energy obtained for the corrosion of mild steel in the blank solution of 0.7M HCl was 20,908.68J while the addition of Voacanga Africana's crushed leaves at 15g per litre of 0.7M HCl increased the activation energy to 26,710.26J. The corrosion inhibition of mild steel in hydrochloric acid by thoroughly crushed leaves of Voacanga Africana obeyed the Langmuir adsorption isotherm with  $R^2 = 0.992$ . The FTIR spectrum of the adhered constituents of Voacanga Africana's crushed leaves on the surface of mild steel coupon immersed at 30g per litre of 0.7M HCl for eight hours revealed the presence of O–H functional group, carbon-carbon triple bond of alkynes and the amide functional group of C=O bond.

## Appendix

Table A1. Prediction of Corrosion Inhibition of Mild Steel in Hydrochloric Acid Medium by thoroughly Crushed Leaves of Voacanga Africana.

Case	Time (h)	Conc_of_H Cl (M)	Quantity_of_VA_Crushed_Leaves(g)	Exp. Corrosion Rate ( $\text{mg.cm}^{-2}.\text{h}^{-1}$ )	Prediction_by_MR		Prediction_by_ANN	
					CR	Error	CR	Error
1	1	0.7	0	2.6487	1.89618	0.75252	1.6837	0.965
2	2	0.7	0	1.8646	1.68281	0.18179	1.3689	0.4957
3	3	0.7	0	1.3989	1.46944	-0.07054	1.2470	0.1519
4	4	0.7	0	1.4137	1.25606	0.15764	1.1939	0.2198
5	5	0.7	0	1.4214	1.04269	0.37871	1.165	0.2564
6	6	0.7	0	1.3684	0.82931	0.53909	1.1446	0.2238
7	7	0.7	0	1.3924	0.61594	0.77646	1.1270	0.2654
8	8	0.7	0	1.3934	0.40257	0.99083	1.1101	0.2833
9	1	0.7	15	1.1908	1.58476	-0.39396	1.1635	0.0273
10	2	0.7	15	0.5751	1.37139	-0.79629	0.9258	-0.3507
11	3	0.7	15	0.4686	1.15801	-0.68941	0.8334	-0.3648
12	4	0.7	15	0.4778	0.94464	-0.46684	0.7903	-0.3125
13	5	0.7	15	0.4008	0.73127	-0.33047	0.7647	-0.3639
14	6	0.7	15	0.3325	0.51789	-0.18539	0.7457	-0.4132
15	7	0.7	15	0.3502	0.30452	0.04568	0.7294	-0.3792
16	8	0.7	15	0.2962	0.09114	0.20506	0.7145	-0.4183
17	1	0.7	30	1.0688	1.27334	-0.20454	0.7781	0.2907
18	2	0.7	30	0.6651	1.05997	-0.39487	0.6295	0.0356
19	3	0.7	30	0.5547	0.84659	-0.29189	0.5760	-0.0213
20	4	0.7	30	0.5322	0.63322	-0.10102	0.5540	-0.0218
21	5	0.7	30	0.4560	0.41985	0.03615	0.5432	-0.0872
22	6	0.7	30	0.5450	0.20647	0.33853	0.5365	0.0085
23	7	0.7	30	0.4373	-0.0069	0.4442	0.5316	-0.0943
24	8	0.7	30	0.4358	-0.22028	0.65608	0.5274	-0.0916
25	1	0.7	45	0.8974	0.96192	-0.06452	0.6769	0.2205
26	2	0.7	45	0.6520	0.74855	-0.09655	0.5547	0.0973

Case	Time (h)	Conc. of H Cl (M)	Quantity of VA Crushed Leaves(g)	Exp. Corrosion Rate (mg.cm <sup>-2</sup> .h <sup>-1</sup> )	Prediction by MR		Prediction by ANN	
					CR	Error	CR	Error
27	3	0.7	45	0.5207	0.53517	-0.01447	0.5128	0.0079
28	4	0.7	45	0.3340	0.3218	0.0122	0.4973	-0.1633
29	5	0.7	45	0.4711	0.10842	0.36268	0.4911	-0.0200
30	6	0.7	45	0.4778	-0.10495	0.58275	0.4883	-0.0105
31	7	0.7	45	0.3925	-0.31832	0.71082	0.4868	-0.0943
32	8	0.7	45	0.3688	-0.5317	0.9005	0.4858	-0.1170
33	1	1.2	0	2.2857	2.21006	0.07564	2.4601	-0.1744
34	2	1.2	0	1.5683	1.99668	-0.42838	1.6580	-0.0897
35	3	1.2	0	1.1109	1.78331	-0.67241	1.3450	-0.2341
36	4	1.2	0	1.1753	1.56994	-0.39464	1.2235	-0.0482
37	5	1.2	0	1.1838	1.35656	-0.17276	1.1700	0.0138
38	6	1.2	0	1.0470	1.14319	-0.09619	1.1405	-0.0935
39	7	1.2	0	1.0447	0.92981	0.11489	1.1194	-0.0747
40	8	1.2	0	0.9276	0.71644	0.21116	1.1010	-0.1734
41	1	1.2	15	1.6351	1.89864	-0.26354	1.7676	-0.1325
42	2	1.2	15	1.0078	1.68526	-0.67746	1.1255	-0.1177
43	3	1.2	15	0.7900	1.47189	-0.68189	0.8951	-0.1051
44	4	1.2	15	0.7493	1.25852	-0.50922	0.8059	-0.0566
45	5	1.2	15	0.6936	1.04514	-0.35154	0.7645	-0.0709
46	6	1.2	15	0.6661	0.83177	-0.16567	0.7401	-0.0740
47	7	1.2	15	0.5838	0.61839	-0.03459	0.7220	-0.1382
48	8	1.2	15	0.582	0.40502	0.17698	0.7067	-0.1247
49	1	1.2	30	1.8007	1.58722	0.21348	1.2070	0.5937
50	2	1.2	30	0.7900	1.37384	-0.58384	0.7653	0.0247
51	3	1.2	30	0.6215	1.16047	-0.53897	0.6198	0.0017
52	4	1.2	30	0.7166	0.9471	-0.23050	0.5677	0.1489
53	5	1.2	30	0.6302	0.73372	-0.10352	0.5465	0.0837
54	6	1.2	30	0.5087	0.52035	-0.01165	0.5362	-0.0275
55	7	1.2	30	0.3004	0.30697	-0.00657	0.5301	-0.2297
56	8	1.2	30	0.3264	0.0936	0.23280	0.5256	-0.1992
57	1	1.2	45	0.6354	1.2758	-0.6404	1.0557	-0.4203
58	2	1.2	45	0.5896	1.06242	-0.47282	0.6749	-0.0853
59	3	1.2	45	0.2962	0.84905	-0.55285	0.553	-0.2568
60	4	1.2	45	0.2127	0.63567	-0.42297	0.5112	-0.2985
61	5	1.2	45	0.4932	0.4223	0.07090	0.4959	-0.0027
62	6	1.2	45	0.4410	0.20893	0.23207	0.4898	-0.0488
63	7	1.2	45	0.2996	-0.00445	0.30405	0.4871	-0.1875
64	8	1.2	45	0.2062	-0.21782	0.42402	0.4857	-0.2795
65	1	2.2	0	5.9626	2.83781	3.12479	5.0362	0.9264
66	2	2.2	0	3.5723	2.62444	0.94786	3.8548	-0.2825
67	3	2.2	0	2.4367	2.41106	0.02564	2.3956	0.0411
68	4	2.2	0	1.9052	2.19769	-0.29249	1.6007	0.3045
69	5	2.2	0	1.5683	1.98431	-0.41601	1.2925	0.2758
70	6	2.2	0	1.3462	1.77094	-0.42474	1.1723	0.1739
71	7	2.2	0	1.2016	1.55757	-0.35597	1.1184	0.0832
72	8	2.2	0	1.1519	1.34419	-0.19229	1.0878	0.0641
73	1	2.2	15	4.5307	2.52639	2.00431	4.5084	0.0223
74	2	2.2	15	2.2131	2.31302	-0.09992	3.0493	-0.8362
75	3	2.2	15	1.4986	2.09964	-0.60104	1.6646	-0.1660
76	4	2.2	15	1.1668	1.88627	-0.71947	1.0536	0.1132
77	5	2.2	15	1.0647	1.67289	-0.60819	0.8377	0.2270
78	6	2.2	15	0.8853	1.45952	-0.57422	0.7549	0.1304
79	7	2.2	15	0.7667	1.24615	-0.47945	0.7170	0.0497
80	8	2.2	15	0.7497	1.03277	-0.28307	0.6950	0.0547
81	1	2.2	30	3.8686	2.21497	1.65363	3.8377	0.0309
82	2	2.2	30	2.1492	2.00159	0.14761	2.3089	-0.1597
83	3	2.2	30	1.6167	1.78822	-0.17152	1.1722	0.4445
84	4	2.2	30	0.8394	1.57485	-0.73545	0.7435	0.0959

Case	Time (h)	Conc. of H Cl (M)	Quantity of VA Crushed Leaves(g)	Exp. Corrosion Rate (mg.cm <sup>-2</sup> .h <sup>-1</sup> )	Prediction by MR		Prediction by ANN	
					CR	Error	CR	Error
85	5	2.2	30	0.6366	1.36147	-0.72487	0.6032	0.0334
86	6	2.2	30	0.6399	1.14810	-0.5082	0.5535	0.0864
87	7	2.2	30	0.6659	0.93472	-0.26882	0.5337	0.1322
88	8	2.2	30	0.5525	0.72135	-0.16885	0.5244	0.0281
89	1	2.2	45	3.793	1.90355	1.88945	3.5951	0.1979
90	2	2.2	45	1.6743	1.69017	-0.01587	2.0981	-0.4238
91	3	2.2	45	1.2072	1.4768	-0.2696	1.0524	0.1548
92	4	2.2	45	0.9817	1.26343	-0.28173	0.6718	0.3099
93	5	2.2	45	1.0363	1.05005	-0.01375	0.5502	0.4861
94	6	2.2	45	0.8853	0.83668	0.04862	0.5086	0.3767
95	7	2.2	45	0.7277	0.6233	0.10440	0.4934	0.2343
96	8	2.2	45	0.6546	0.40993	0.24467	0.4875	0.1671

## References

- [1] Bartholomew, R. D., & Shelfler, D. A. (1996). Corrosion. Avallone, E. A., Baumeister III, T., (Eds), Marks' standard handbook for Mechanical Engineering, (10<sup>th</sup> Ed., pp. 6-(95-107). New York: Mc-Graw Hill.
- [2] Sharma, B. K. (2011). Industrial Chemistry [Including Chemical Engineering]. India: Krishna Press, p. 1698-1708.
- [3] Chong, C. V. Y. (1981). Properties of Materials (p. 224-230). Britain: Chaucer Press.
- [4] Lagrenée M., Mernari, B., Bouanis M., Traisnel M., & Bentiss F. (2002). Study of the mechanism and inhibiting efficiency of 3, 5-bis (4-methylthiophenyl)-4H-1, 2, 4-triazole on mild steel corrosion in acidic media. Corros Sci. 44, 573-588.
- [5] Su, J. O, Jeongim, P., Min, J. L., So, Y. P., & Kyungho, C. (2006). Ecological hazard assessment of major veterinary benzimidazoles: Acute and chronic toxicities to aquatic microbes and invertebrates. EnvTox Chem. 25, 2221-2226.
- [6] Minling, G., Wenhua, S., & Xiaoying, C. (2010). The acute toxicity of triazoles to earthworms using a simple paper contact method. 4th Intl. Conf. Bioinform. Biomed. Engg DOI 10.1109/ICBBE. 2010.5515198.
- [7] Martin, M. T., Brennan, R. J., Hu, W., Ayanoglu, E., Lau, C., Ren, H., Wood, C. R., Corton, J. C., Kavlock, R. J., & Dix, D. J. (2007). Toxicogenomic study of triazole fungicides and perfluoroalkyl acids in rat livers predicts toxicity and categorizes chemicals based on mechanism of toxicity. Toxicol Sci. 97, 595- 613.
- [8] Hofmann, A., Ratsch, C., & Shultes, R. (1992). Plants of Gods: Their Sacred, Healing, and Hallucination Powers. USA: Healing Arts press.
- [9] Ndukwe, A. I. and Anyakwo, C. N. (2017). Modelling of Corrosion Inhibition of Mild Steel in Sulphuric Acid by thoroughly Crushed Leaves of Voacanga Africana (Apocynaceae). AJER, 6 (1), 344-356. [http://www.ajer.org/papers/v6\(01\)/ZX060344356.pdf](http://www.ajer.org/papers/v6(01)/ZX060344356.pdf)
- [10] Cleversley, K., (n.d.). Retrieved May 3, 2015, from <http://www.entheology.com/plants/vocanga-vocanga>
- [11] Neural Networks (2012). ANN - Artificial Neural Networks. Engineering Garage. Retrieved May 27, 2017 from <https://www.engineersgarage.com/articles/artificial-neural-networks>
- [12] Khadom, A. A. (2014). Effect of Temperature on Corrosion Inhibition of Copper - Nickel Alloy by Tetra-ethylenepentamine underflow Conditions. Journal of the Chilean Chemical Society, 59 (3), 2545-2549.
- [13] Negnevitsky, M. (2005) Artificial Intelligence, A guide to Intelligence Systems. Retrieved January 3, 2016 from [http://www.academia.dk/BiologiskAntropologi/Epidemiologi/DataMining/Artificial\\_Intelligence-A\\_Guide\\_to\\_Intelligent\\_Systems.pdf](http://www.academia.dk/BiologiskAntropologi/Epidemiologi/DataMining/Artificial_Intelligence-A_Guide_to_Intelligent_Systems.pdf)
- [14] Nasr, M. S., Moustafa, M. A. E., Seif, H. A. E., & El Kobrosy, G. (2012). Application of Artificial Neural Network (ANN) for the prediction of EL-AGAMY waste water treatment plant performance- EGYPT. Alexandria Engineering Journal 51, 37-43.