

Direct Synthesis of Diethyl Carbonate from CO₂ over ZnO@Na₃PW₁₂O₄₀ Heterogeneous Material

Meng Zhang

School of Biomedical Engineering, Southern Medical University, Guangzhou, China

Email address:

zhangmeng@smu.edu.cn

To cite this article:

Meng Zhang. Direct Synthesis of Diethyl Carbonate from CO₂ over ZnO@Na₃PW₁₂O₄₀ Heterogeneous Material. *Science Journal of Chemistry*.

Special Issue: *The Application of Catalytic Materials, Polymers and Li Batteries in New Energy and Environmental Protection*.

Vol. 7, No. 6, 2019, pp. 105-109. doi: 10.11648/j.sjc.2019070611

Received: November 4, 2019; **Accepted:** November 26, 2019; **Published:** December 4, 2019

Abstract: At present, the world is facing two major problems: energy crisis and CO₂ emission. Diethyl carbonate is an effective gasoline additive which can greatly improve octane number. The route of diethyl carbonate synthesis from CO₂ is green and economical technique, which can effectively solve both energy crisis and CO₂ emission problems together. However, the design and preparation of catalysts is the core and key to realize the conversion from CO₂ to diethyl carbonate. This paper mainly described a novel synthesis of ZnO@Na₃PW₁₂O₄₀ heterogeneous material that applied in the direct synthesis of diethyl carbonate from CO₂ and ethanol. The special pore and channel structure of Na₃PW₁₂O₄₀ was used to maximize the catalytic capacity of ZnO material. The prepared catalysts were fully characterized by means of temperature-programmed desorption (TPD) and X-ray powder diffraction (XRD). The properties of acid-base sites on the surface of ZnO@Na₃PW₁₂O₄₀ were measured by temperature-programmed desorption technique. The catalytic performance over ZnO@Na₃PW₁₂O₄₀ heterogeneous material was examined on micro-reactor. The experiment results indicated that synthesized novel ZnO@Na₃PW₁₂O₄₀ heterogeneous material had large number of acid-base sites and high catalytic activity. This novel ZnO@Na₃PW₁₂O₄₀ catalyst had great ability to realize the effective conversion from CO₂ to diethyl carbonate. This technology not only improved the utilization rate of energy materials, but also reduced CO₂ emissions.

Keywords: Carbon Dioxide, Diethyl Carbonate, Material, Ethanol, Heterogeneous

1. Introduction

Diethyl carbonate (DEC) have attracted widespread attention during the last ten years due to its extensive industrial applications [1-3]. DEC is a type of good green solvent [4, 5] instead of phosgene, dimethyl sulphate and alkyl halide. And DEC is a kind of good electrolyte in lithium ion batteries [6-9]. More importantly, DEC can be used as an ideal additive for gasoline in order to increase octane number of gasoline [10-12]. Recently, DEC can be synthesized by several routes: phosgenation of ethanol [13, 14], oxidative carbonylation of ethanol [15-17], transesterification of organic carbonates [18-20], direct synthesis from CO₂ and ethanol, among which the last route is particularly promising due to cost effectiveness, mild reaction conditions and safe operations. Furthermore, this process involves the activation of CO₂ resulting in very low

conversion yield. Therefore, the exploration of highly efficient, stable catalysts is desirable. Many literatures [21-26] have shown that both acid sites and base sites are crucial to determine the catalytic activity. Yet, the cooperation of acid-base sites as well as their respective contribution to catalytic activity is not confirmed. Therefore, how to adjust the acid-base sites of catalysts in order to obtain high stable and efficient catalysts is still a challenge.

In this work, a novel heterogeneous material of ZnO@Na₃PW₁₂O₄₀ catalyst was synthesized. After temperature-programmed desorption (TPD) measurement, on the surface of ZnO@Na₃PW₁₂O₄₀ catalyst there were many acid and base sites that were enough to make CO₂ and ethanol activated. According to catalytic performance results, this heterogeneous material had high activity for CO₂ conversion to DEC.

2. Experimental

2.1. Catalysts Preparation

Prepare the ammonia solution of octyl nitrate, in which Zn is 0.4mol/L. The ammonia complex solution of zinc nitrate is placed in the spray bottle of 75mL. Take a glass plate and lay aluminum foil on the glass plate. Evenly sprinkle Na₃PW₁₂O₄₀ powder on the aluminum foil, and place an infrared lamp beside it. Intermittently spray of powdered samples on aluminum foil with spray bottle. Put in the oven and dry at 100°C. The precursor of the catalyst is obtained by grinding in an agate mortar and sieving through a 200 mesh sieve. Put it into muffle furnace and calcine it at 500°C for 6 hours under air atmosphere. The final ZnO@Na₃PW₁₂O₄₀ heterogeneous material is obtained.

2.2. Catalytic Characterization

2.2.1. Powder X-ray Diffraction (XRD)

The X-ray diffraction was obtained on Rigaku Dmax 2200 diffractometer with graphite monochromatized Cu K α radiation ($\lambda=0.154178\text{nm}$) at 40kV and 20mA. The sample was scanned from 5° to 80° at a rate of 3°/min. The crystallite sizes of the particles were calculated from the XRD peaks using the Scherrer equation.

2.2.2. Temperature Programmed Desorption (TPD)

Temperature programmed desorption (TPD) was obtained on Quanta ChromChem 3000 to determine the surface acid-base properties of catalysts. Before adsorption experiments, 0.1g of the samples were pretreated at 120°C in a quartz U-tube in a nitrogen flow with a flow rate of 50 mL per minute for 2h to remove absorbed water. Upon cooling to room temperature, the samples were saturated with 10%CO₂/90%N₂, 10%NH₃/90%N₂ for 1 h. Then the physical adsorbed CO₂, NH₃ were removed by streaming with 30%N₂/70% He for 3h under a flow rate of 50mL/min. The samples were then heated up to 500°C at a heating rate of 4°C/min in N₂/He under a flow rate of 80mL/min.

2.3. Catalytic Evaluations

Synthesis of DEC from ethanol and CO₂ was carried out in a continuous fixed-bed reactor. N₂ was purged into reactor to replace the air inside before the reaction temperature was heated up to a set temperature. CO₂ was purged into ethanol container to get CO₂/ethanol mixed gas. The mixed gas was then charged into the reactor. The resultants of the reaction were measured by GC-112N equipped with a flame ionization detector (FID) through a six-way valve to connect with the reactor.

3. Results and Discussion

3.1. Structure Characterization

XRD patterns of synthesized ZnO@Na₃PW₁₂O₄₀ heterogeneous material was shown in Figure 1. The main peak

was around 8.0 degree and all the peaks belonged to the characteristic peaks of Na₃PW₁₂O₄₀. There were no peaks of ZnO in the XRD pattern, which was due to excellent dispersion of ZnO particles.

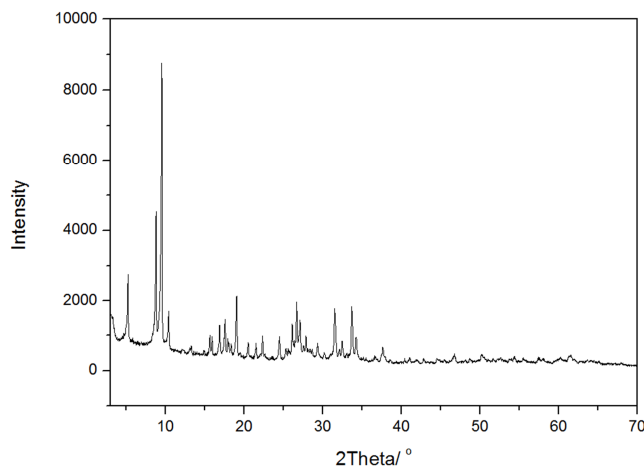


Figure 1. XRD pattern of ZnO@Na₃PW₁₂O₄₀ Heterogeneous Material.

3.2. Lewis Acid-base Characterization

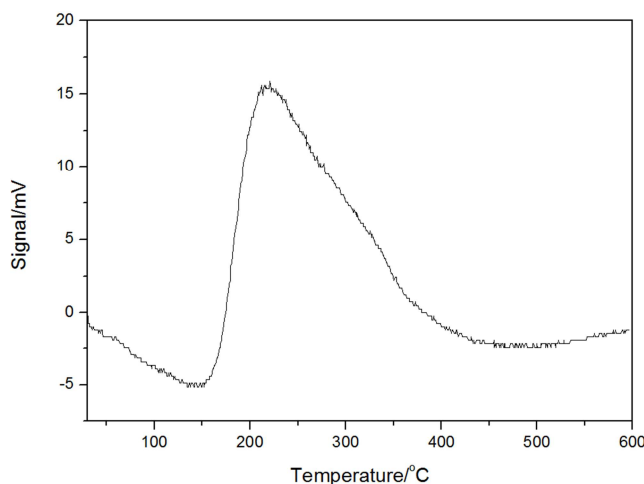


Figure 2. CO₂-TPD pattern of ZnO@Na₃PW₁₂O₄₀ Heterogeneous Material.

To investigate the base sites characteristics of ZnO@Na₃PW₁₂O₄₀ material, CO₂-TPD was measured as shown in Figure 2. The amount of peaks stands for types of base sites on the surface of ZnO@Na₃PW₁₂O₄₀ material. Peaks from 100°C to 300°C, it is weak base site. Peaks from 300°C to 500°C, it is moderate base site. Peaks from 500°C to 700°C, it is strong base site. The area of peaks stands for numbers of a certain type of base site. According to measured CO₂-TPD pattern, there was only one big peak around 240°C, which indicates that only one type of weak base site exists on the surface of synthesized ZnO@Na₃PW₁₂O₄₀ material. The area of peak was large, which indicates that there are a large number of weak base sites. The CO₂-TPD pattern implied that synthesized ZnO@Na₃PW₁₂O₄₀ material had the ability to make CO₂ activated.

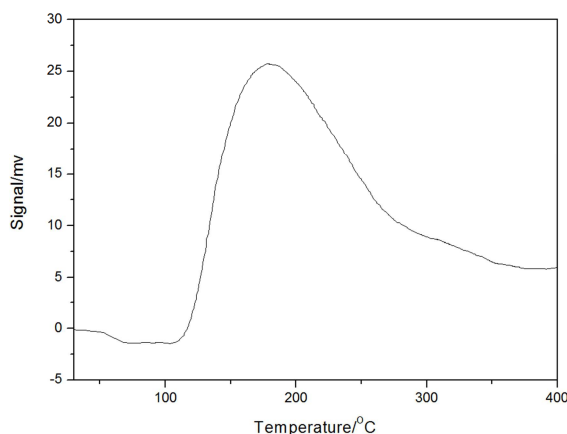


Figure 3. NH_3 -TPD pattern of $\text{ZnO}@Na_3PW_{12}O_{40}$ Heterogeneous Material.

To investigate the acid sites characteristics of $\text{ZnO}@Na_3PW_{12}O_{40}$ material, NH_3 -TPD was measured as shown in Figure 3. The amount of peaks stands for types of acid sites on the surface of $\text{ZnO}@Na_3PW_{12}O_{40}$ material. Peaks from 100°C to 300°C, it is weak acid site. Peaks from 300°C to 500°C, it is moderate acid site. Peaks from 500°C to 700°C, it is strong acid

site. The area of peaks stands for numbers of a certain type of acid site. According to measured NH_3 -TPD pattern, there was only one big peak around 170°C, which indicates that only one type of weak acid site exists on the surface of synthesized $\text{ZnO}@Na_3PW_{12}O_{40}$ material. The area of peak was large, which indicates that there are a large number of weak acid sites. Different from CO_2 -TPD, NH_3 was used instead of base reactants to measure the acid sites of catalysts. The NH_3 -TPD pattern implied that synthesized $\text{ZnO}@Na_3PW_{12}O_{40}$ material had the ability to make ethanol activated.

3.3. Performance of Catalyst

Different reaction temperature was measured for direct synthesis of diethyl carbonate from CO_2 over synthesized $\text{ZnO}@Na_3PW_{12}O_{40}$ material. According to experimental results as shown in Table 1, the best ethanol conversion was 0.89% and the best DEC selectivity was 94.2% when reaction temperature was 140°C. Totally, ethanol conversion was less than 1% and DEC selectivity was more than 90%.

Table 1. Direct synthesis of diethyl carbonate from CO_2 over $\text{ZnO}@Na_3PW_{12}O_{40}$ on conditions of different reaction temperature.

Temperature/°C	Ethanol Conversion/%	DEC Selectivity/%	DEC Yield/%
80	0.13	90.1	0.12
100	0.44	90.9	0.40
120	0.51	92.3	0.47
140	0.89	94.2	0.84
160	0.62	91.6	0.57

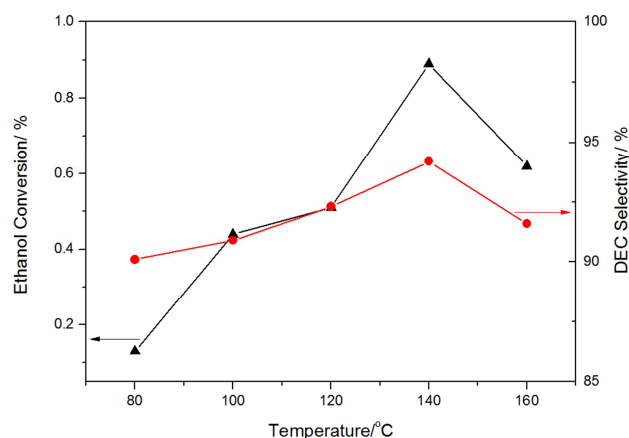


Figure 4. Direct synthesis of diethyl carbonate from CO_2 over $\text{ZnO}@Na_3PW_{12}O_{40}$ on conditions of different reaction temperature.

In order to study the rule of catalytic activity with reaction temperature more clearly, Figure 4 was drawn based on experimental results. Clearly, ethanol conversion was increased with the increasing reaction temperature. Beyond 140°C, ethanol conversion started to decline. DEC selectivity was improved with the increasing reaction temperature.

Different reaction pressure was measured for direct synthesis of diethyl carbonate from CO_2 over synthesized $\text{ZnO}@Na_3PW_{12}O_{40}$ material. According to experiment results as shown in Table 2, the best ethanol conversion was 0.89% and the best DEC selectivity was 94.2% when reaction

pressure was 2.0 MPa. Totally, ethanol conversion was less than 0.9% and DEC selectivity was more than 90%.

Table 2. Direct synthesis of diethyl carbonate from CO_2 over $\text{ZnO}@Na_3PW_{12}O_{40}$ on conditions of different reaction pressure.

Pressure/MPa	Ethanol Conversion/%	DEC Selectivity/%	DEC Yield/%
0.8	0.11	90.8	0.10
1.2	0.43	93.2	0.40
1.6	0.66	94.1	0.62
2.0	0.89	94.2	0.84
2.4	0.59	95.4	0.56
2.8	0.32	93.7	0.30

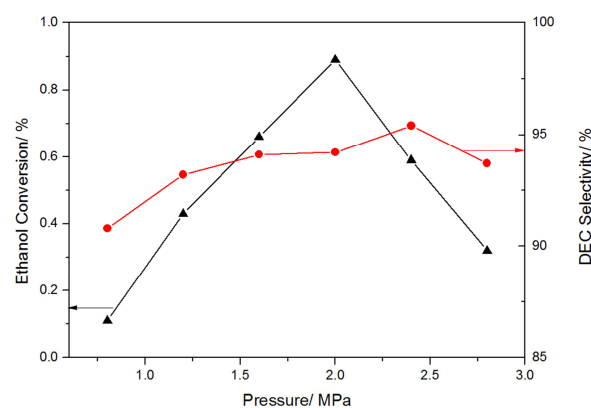


Figure 5. Direct synthesis of diethyl carbonate from CO_2 over $\text{ZnO}@Na_3PW_{12}O_{40}$ on conditions of different reaction pressure.

In order to study the rule of catalytic activity with reaction pressure more clearly, Figure 5 was drawn based on experimental results. Clearly, ethanol conversion was increased with the increasing reaction pressure. Beyond 2.0 MPa, ethanol conversion started to decline. DEC selectivity was improved slightly with the increasing reaction pressure.

4. Conclusions

Heterogeneous material of ZnO@Na₃PW₁₂O₄₀ catalyst was successfully synthesized by a novel method. According to temperature-programmed desorption (TPD) measurement, there was only one type of weak acid site and a type of weak base site on the surface of ZnO@Na₃PW₁₂O₄₀ catalyst. And the amount of weak acid sites and weak base sites was much large, which indicated that synthesized ZnO@Na₃PW₁₂O₄₀ material had the ability to make both CO₂ and ethanol activated. The catalytic performance of ZnO@Na₃PW₁₂O₄₀ heterogeneous material was measured on micro-reactor. The best ethanol conversion was 0.89% and DEC selectivity was 94.2% on conditions of reaction temperature 140°C and pressure 2.0 MPa.

Conflicts of Interest

There are no conflicts of interest to declare.

References

- [1] Y. Yoshida, Y. Arai, S. Kado, K. Kunimori, K. Tomishige, Direct synthesis of organic carbonates from the reaction of CO₂ with methanol and ethanol over CeO₂ catalysts, *Catal. Today*, 2006, 115, 95-101.
- [2] D. N. Briggs, K. H. Lawrence, A. T. Bell, An investigation of carbon-supported CuCl₂/PdCl₂ catalysts for diethyl carbonate synthesis, *Appl. Catal A-Gen*, 2009, 366, 71-83.
- [3] M. Honda, S. Kuno, N. Begum, K. Fujimoto, K. Suzuki, Y. Nakagawa, K. Tomishige, Catalytic synthesis of dialkyl carbonate from low pressure CO₂ and alcohols combined with acetonitrile hydration catalyzed by CeO₂, *Appl. Catal A-Gen*, 2010, 384, 165-170.
- [4] D. N. Briggs, G. Bong, E. Leong, K. Oei, G. Lestari, A. Bell, Effects of support composition and pretreatment on the activity and selectivity of carbon-supported PdCu_nCl_x catalysts for the synthesis of diethyl carbonate, *J. Catal.*, 2010, 276, 215-228.
- [5] E. Leino, P. Arvela, K. Eränen, M. Tenho, D. Murzin, T. Salmi, J. Mikkola, Enhanced yields of diethyl carbonate via one-pot synthesis from ethanol, carbon dioxide and butylene oxide over cerium (IV) oxide, *Chem. Engine. J.*, 2011, 176, 124-133.
- [6] M. Zhang, M. Xiao, S. Wang, D. Han, Y. Lu, Y. Meng, Cerium oxide-based catalysts made by template-precipitation for the dimethyl carbonate synthesis from Carbon dioxide and methanol, *J. Clean. Prod.*, 2015, 103, 847-853.
- [7] M. Zhang, Z. Fu, M. Xiao, Y. Yu, S. Wang, M. Choi, Y. Meng, Synthesis of Co_{1.5}PW₁₂O₄₀ and its catalytic performance of completely converting methanol to ethylene, *Chem. Comm.*, 2016, 52, 1151.
- [8] M. Zhang, K. A. Alferov, M. Xiao, D. Han, S. Wang, Y. Meng, Continuous Dimethyl Carbonate Synthesis from CO₂ and Methanol Using Cu-Ni@VSiO as Catalyst Synthesized by a Novel Sulfuration Method, *Catalysts*, 2018, 8, 142.
- [9] O. Arbela'ez, A. Orrego, F. Bustamante, A. L. Villa, Direct Synthesis of Diethyl Carbonate from CO₂ and CH₃CH₂OH Over Cu-Ni/AC Catalyst, *Top Catal.*, 2012, 55, 668-672.
- [10] M. Tamura, M. Honda, K. Noro, Y. Nakagawa, K. Tomishige, Heterogeneous CeO₂-catalyzed selective synthesis of cyclic carbamates from CO₂ and aminoalcohols in acetonitrile solvent, *J. Catal.*, 2013, 305, 191-203.
- [11] L. Wang, H. Li, S. Xin, P. He, Y. Cao, F. Li, X. Hou, Highly efficient synthesis of diethyl carbonate via one-pot reaction from carbon dioxide, epoxides and ethanol over KI-based binary catalyst system, *Appl. Catal A-Gen*, 2014, 471, 19-27.
- [12] Y. Lim, X. Wang, E. Park, H. Jang, Direct Coupling of Cs₂CO₃ and Alcohols for the Synthesis of Dimethyl, Diethyl, and Various Dialkyl Carbonates, *Bull. Korean Chem. Soc.* 2014, 35, No. 2.
- [13] X. Zhang, D. Jia, J. Zhang, Y. Sun, Direct Synthesis of Diethyl Carbonate from CO₂ and Ethanol Catalyzed by ZrO₂/Molecular Sieve, *Catal. Lett.*, 2014, 144, 2144-2150.
- [14] S. Xin, L. Wang, H. Li, K. Huang, F. Li, Synthesis of diethyl carbonate from urea and ethanol over lanthanum oxide as a heterogeneous basic catalyst, *Fuel Process. Technol.*, 2014, 126, 453-459.
- [15] M. Honda, M. Tamura, Y. Nakagawa, K. Nakao, K. Suzuki, K. Tomishige, Organic carbonate synthesis from CO₂ and alcohol over CeO₂ with 2-cyanopyridine: Scope and mechanistic studies, *J. Catal.*, 2014, 318, 95-107.
- [16] D. Wang, X. Zhang, C. Liu, T. Cheng, W. Wei, Y. Sun, Transition metal-modified mesoporous Mg-Al mixed oxides: Stable base catalysts for the synthesis of diethyl carbonate from ethyl carbamate and ethanol, *Appl. Catal A-Gen*, 2015, 505, 478-486.
- [17] L. Prymak, V. Kalevaru, S. Wohlrab, A. Martin, Continuous synthesis of diethyl carbonate from ethanol and CO₂ over Ce-Zr-O catalysts, *Catal. Sci. & Technol.*, 2015, 5, 2322.
- [18] M. Tamura, T. Kitanaka, Y. Nakagawa, K. Tomishige, Cu Sub-Nanoparticles on Cu/CeO₂ as an Effective Catalyst for Methanol Synthesis from Organic Carbonate by Hydrogenation, *ACS Catal.*, 2016, 6, 376-380.
- [19] O. Arbela'ez, A. Orrego, F. Bustamante, A. Villa, Effect of Acidity, Basicity and ZrO₂ Phases of Cu-Ni/ZrO₂ Catalysts on the Direct Synthesis of Diethyl Carbonate from CO₂ and Ethanol, *Catal. Lett.*, 2016, 146, 725-733.
- [20] Y. Wang, D. Jia, Z. Zhu, Y. Sun, Synthesis of Diethyl Carbonate from Carbon Dioxide, Propylene Oxide and Ethanol over KNO₃-CeO₂ and KBr-KNO₃-CeO₂ Catalysts, *Catalysts*, 2016, 6, 52.
- [21] J. Wang, Z. Hao, S. Wohlrab, Continuous CO₂ esterification to diethyl carbonate (DEC) at atmospheric pressure: application of porous membranes for in situ H₂O removal, *Green Chem.*, 2017, 19, 3595.
- [22] H. Iida, R. Kawaguchi, K. Okumura, Production of diethyl carbonate from ethylene carbonate and ethanol over supported fluoro-perovskite catalysts, *Catal. Commu.*, 2018, 108, 7-11.

- [23] E. Leino, N. Leino, P. Arvela, A. Rautio, J. Dahl, J. Roine, J. Mikkola, Synthesis and characterization of ceria-supported catalysts for carbon dioxide transformation to diethyl carbonate, *Catal. Today*, 2018, 306, 128-137.
- [24] M. Chai, W. Zhao, G. Li, S. Xu, Q. Jia, Y. Chen, Novel SO₂ Phase-Change Absorbent: Mixture of N,N-Dimethylaniline and Liquid Paraffin, *Ind. Eng. Chem. Res.* 2018, 57, 12502–12510.
- [25] T. Yan, W. Bing, M. Xu, Y. Li, Y. Yang, G. Cui, L. Yang, M. Wei, Acid–base sites synergistic catalysis over Mg–Zr–Al mixed metal oxide toward synthesis of diethyl carbonate, *RSC Adv.*, 2018, 8, 4695.
- [26] O. Arbela'ez, E. Herna'ndez, L. M. Gonza'lez, F. Bustamante, A. L. Villa, Enhanced Conversion in the Direct Synthesis of Diethyl Carbonate from Ethanol and CO₂ by Process Intensification, *Chem. Eng. Technol.*, 2019, 42, 1135–1143.